

^{a)}Electronic mail: Caterina.Braggio@unipd.it

photons per MeV. A light yield of $(79 \pm 8) \times 10^3$ has also been observed in YAG:(10%)Yb³⁺, whose emission peaked around $\lambda = 1.03 \mu\text{m}$ ¹⁴.

In addition, if we choose a material with a low energy level ($E_1 \sim 10 - 100 \text{ meV}$, corresponding to the wavelength range $\sim 100 - 10 \mu\text{m}$) characterized by a long lifetime, such metastable level acts as a reservoir in which the energy of the particle can be stored and converted in fluorescent photons by the pump laser. In view of the previous hypotheses, and provided the efficiency of the upconversion process is high^{15,16}, the proposed scheme has the potential to generate a greater number of information carriers (photons) for a given energy release.

The present work is organized as follows. We first investigate the response of a low concentrated YAG:(0.5%)Er³⁺ crystal to an electron gun excitation, which represent our particle signal in Fig. 1. These preliminary measurements include both the acquisition of cathodoluminescence (CL) spectra and the study of the $^4I_{13/2}$ metastable lifetime. We also estimate the efficiency of the laser-pumped YAG:Er crystal in the counting of photons delivered by a diode laser ($\lambda \approx 960 \text{ nm}$). The core of the work is the study of the fluorescence stemming from the de-excitation of the $^4S_{3/2}$ level when the particle-excited crystal is continuously pumped by a laser resonant with the transition $^4I_{13/2} \rightarrow ^4S_{3/2}$.

During the CL measurements the YAG:Er crystal, a cylinder of 5 mm diameter and height 3 mm, is mounted at the far end of the electron gun vacuum chamber that is enclosed inside a Pb-shielded cabinet¹⁷. The main transitions involved in the excitation process can be identified in the spectra shown in Fig. 2. The visible spectrum is obtained with a CCD spectrometer (Ocean Optics mod. Red Tide 650), whereas the infrared portion

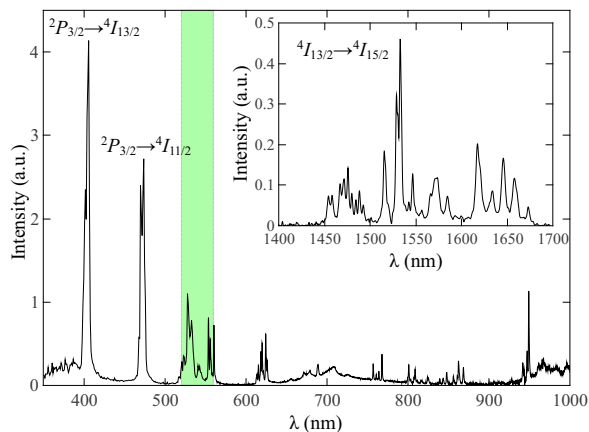


FIG. 2. CL spectra of YAG:Er. The results of Fourier transform interferometer (FT-IR) measurements are displayed in the inset.

of the spectrum, displayed in the inset, is studied with a Fourier transform interferometer (Bruker Equinox 55). The interferometer is equipped with an InGaAs photodi-

ode, sensitive in the range $0.8 - 1.7 \mu\text{m}$. The two sharp emission lines observed in the visible are doublets peaking at 401.5, 405.1 nm and at 470.9, 474.0 nm. They are attributed to $4f - 4f$ transitions of the Er³⁺ ions in the YAG host, respectively to intermanifold transitions $^2P_{3/2} \rightarrow ^4I_{13/2}$ and $^2P_{3/2} \rightarrow ^4I_{11/2}$. These transitions indicate that the metastable level $^4I_{13/2}$ population is increased also by the decay of higher levels excited by electron impact.

As far as the 540 nm band luminescence is concerned, CL spectra in YAG:Er single crystalline films have very recently been reported that show a larger emission¹⁸ than in the present case. This might indicate that a portion of our 540 nm fluorescence band is absorbed in the 3 mm-thick crystal, where the electrons interaction region is limited to a few hundred μm ¹⁹ from the surface while light detection is accomplished on the opposite crystal face.

In the inset we show the infrared spectrum originating from the decay of the $^4I_{13/2}$ metastable level. This manifold around $1.53 \mu\text{m}$ is widely used for IR lasing²⁰. The lifetime of this level is several milliseconds long and weakly depends on the crystal preparation and excitation source. Therefore we have recorded, as shown in Fig. 3, the time evolution of the fluorescence emitted by

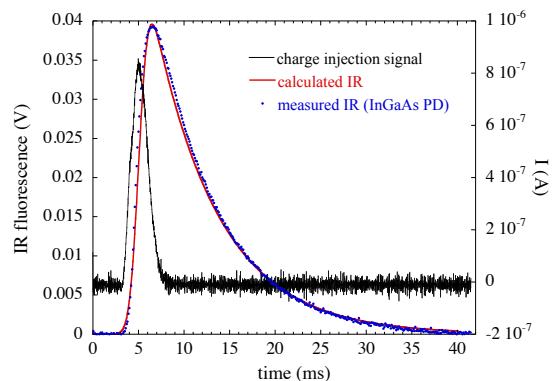


FIG. 3. Electron current waveform (right scale) and the $1.53 \mu\text{m}$ fluorescence signal (left scale) detected by an InGaAs photodiode with input bandpass filter centered at $\lambda = 1.490 \pm 0.25 \mu\text{m}$.

the crystal excited with a 2.5 ms-duration electron pulse. The crystal response has been numerically computed by solving a first order kinetic equation for the population of the level excited by the current pulse shown in the figure. We obtain a lifetime value $\tau = 7.19 \pm 0.02 \text{ ms}$, in fair agreement with literature data²¹⁻²³ obtained with optical excitation.

To study the IRQC efficiency, we have used as infrared source a 960 nm wavelength diode laser. Upconversion is accomplished by pumping the $^4I_{13/2} \rightarrow ^4S_{3/2}$ transition with a tunable Ti:Al₂O₃ laser. In Fig. 4 the fluorescence spectrum, obtained with a CCD spectrometer (Ocean Optics mod. Red), around 540 nm is reported.

We estimate that the IRQC efficiency is of the order of

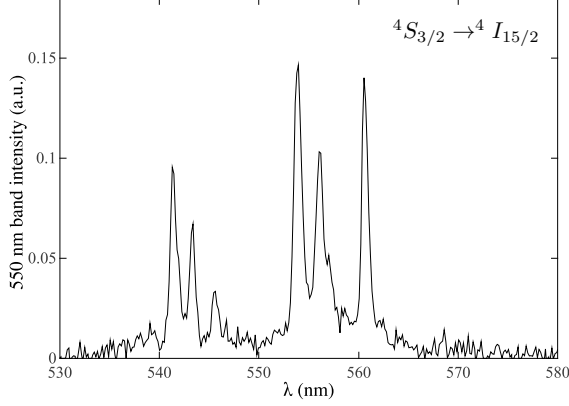


FIG. 4. 540 nm fluorescence spectrum originating from the double resonance with a laser diode at wavelength 960 nm and a Ti:Al₂O₃ laser.

10^{-4} with a pump flux of the order of 10 W/cm^2 . Such a low efficiency is related to the properties of the host material, as reported in Ref. 24.

The experimental apparatus depicted in Fig. 5 was designed to test the particle detection through the IRQC scheme. A few hundred nA continuous current of 60 keV electrons impinges on the YAG:Er crystal while a Ti:Al₂O₃ laser pumped the transition $^4I_{13/2} \rightarrow ^4S_{3/2}$ as shown in the energy level scheme in Fig. 1. Pump light was allowed to impinge on the crystal by means of a 1.6 mm diameter multimode fiber. Detection of the

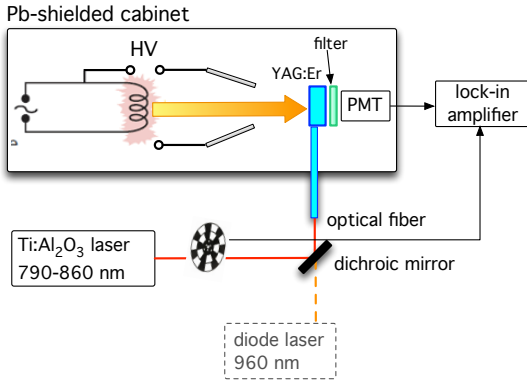


FIG. 5. Scheme of the experimental apparatus for particle detection. The output of a tunable Ti:Al₂O₃ laser is sent through a fiber to pump an YAG:Er crystal irradiated by $\sim 60 \text{ keV}$ electrons. In the preliminary measurements, radiation at a wavelength of $\lambda = 960 \text{ nm}$ is coupled to the crystal together with the pump radiation in order to study the 540 nm fluorescence band.

fluorescence for the different laser pump wavelengths is accomplished by means of a lock-in amplifier connected to the output of a photomultiplier tube (PMT) and mod-

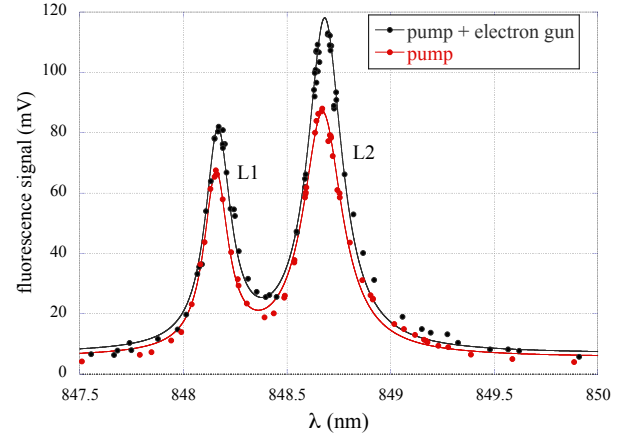


FIG. 6. Demonstration of the novel detector based on the IRQC concept: the 540 nm band fluorescence signal versus pump laser wavelength is greater when the electron gun excites the crystal.

TABLE I. Results of the Lorentzian fit. w and a are respectively the width of the peaks, and their area.

		λ_{max}	w	a
L1	pump	848.16 ± 0.01	0.14 ± 0.01	12.8 ± 0.8
	pump + e^- gun	848.17 ± 0.02	0.15 ± 0.01	16.5 ± 1.1
L2	pump	848.67 ± 0.01	0.23 ± 0.01	28.8 ± 1.1
	pump + e^- gun	848.68 ± 0.01	0.2 ± 0.01	34.8 ± 1.1

ulation of the intensity of the pump laser. A bandpass filter allows the PMT to collect the total intensity emitted only in the range 540-560 nm.

In Fig. 6 the $^4S_{3/2}$ fluorescence intensity is plotted for different wavelengths of the pump laser. The measurement is repeated in the same conditions with the electron gun switched off in order to quantify the contribution of the double resonance with the pump laser only. The interaction of the electrons in the YAG:Er crystal can be discerned due to a 30% increase of the areas under the Lorentzian curves. It is worth noticing that the contribution to the overall fluorescence due to the electrons excitation is geometrically unfavorable as compared to the laser double resonance because of the electron short range in the crystal and of the crystal absorption. Results of the double Lorentzian fit of the data are resumed in Table I. As we apply lock-in techniques through a modulation of the pump signal, it is straightforward that no signal above the PMT threshold is detected when the electron gun is on. The two lines correspond to two well defined transitions⁷ between sublevels in the $^4I_{13/2}$ and the $^4S_{3/2}$ manifolds. We have also checked that the fluorescence signal depends linearly on the electron gun current in a range $0.1 - 1.6 \mu\text{A}$, as shown in Fig. 7. It is linear with the pump as well (Fig. 8), as observed up to the maximum available light intensity ($\sim 280 \text{ mW}$).

In conclusion, we have shown that a laser-pumped

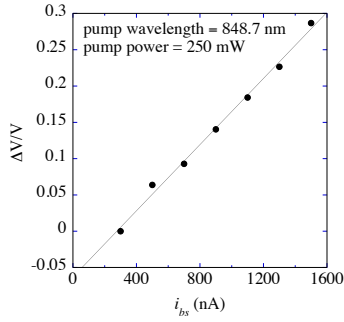


FIG. 7. The relative increase of the 540 nm band intensity ΔV is linearly dependent on the current measured at the beam stopper.

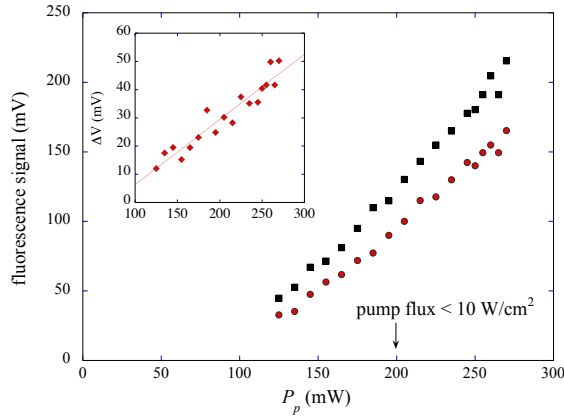


FIG. 8. Linear dependence of the fluorescence on the incident power. The filled dot symbol correspond to the data of the double resonance with the pump laser only, the filled squares represent the combination of the electron gun and the pump laser.

Er^{3+} -doped crystal emits a fluorescence signal in the 540 nm band whose intensity is proportional to the energy deposited in the crystal. To the best of our knowledge, the results presented in this work represent the first demonstration of an IRQC scheme applied to the detection of particles. Such an encouraging result has been obtained in YAG:Er, a crystal that for our purposes cannot be considered as ideal. The optimum crystal is preferably transparent to the pump until a particle interacts in the activated material and deposits its energy in the volume shined by the pump laser. This is not the present case, as shown in Fig. 6, where a significant fraction of the fluorescence is determined by the double resonance with the pump laser. Moreover, the host crys-

tal (YAG) gives a much weaker IRQC output than in fluoride or tungstate hosts²⁴. Another key requirement is the lifetime of the metastable level, and materials characterized by a much longer τ have been recently investigated, such as neodymium doped potassium lead bromide ($\text{KPb}_2\text{Br}_5:\text{Nd}$) in which $\tau = 57$ ms at 15 K²⁵. This material presents another interesting aspect, because of its fluorescence at 1064 nm that decays to the metastable level $^4I_{11/2}$, offering the possibility to exploit looping cycles to increase the detection sensitivity²⁶.

- ¹P. Sikivie, Phys. Rev. Lett. **113**, 201301– (2014).
- ²A. C. Dodd, E. Papageorgiu, and S. Ranfone, Phys. Lett. B **266**, 434–438 (1991).
- ³D. Z. Freedman, Phys. Rev. D **9**, 1389–1392 (1974).
- ⁴C. E. Aalseth, P. S. Barbeau, N. S. Bowden, B. Cabrera-Palmer, J. Colaresi, J. I. Collar, S. Dazeley, P. de Lurgio, J. E. Fast, N. Fields, C. H. Greenberg, T. W. Hossbach, M. E. Keillor, J. D. Kephart, M. G. Marino, H. S. Miley, M. L. Miller, J. L. Orrell, D. C. Radford, D. Reyna, O. Tench, T. D. Van Wechel, J. F. Wilkerson, and K. M. Yocum, Phys. Rev. Lett. **106**, 131301– (2011).
- ⁵C. Enss, *Cryogenic Particle Detection* (Springer-Verlag Berlin Heidelberg, 2005).
- ⁶N. Bloembergen, Phys. Rev. Lett. **2**, 84 (1959).
- ⁷A. K. Kaminskii, *Laser crystals* (Springer-Verlag Berlin, 1981).
- ⁸J. B. Gruber, J. R. Quagliano, M. F. Reid, F. S. Richardson, M. E. Hills, M. D. Seltzer, S. B. Stevens, C. A. Morrison, and T. H. Allik, Phys. Rev. B **48**, 15561–15573 (1993).
- ⁹P. A. Rodnyi, (CRC Press LLC, 1997).
- ¹⁰M. J. Weber, J. Lumin. **100**, 35 – 45 (2002).
- ¹¹W. Drozdowski, P. Dorenbos, J. de Haas, R. Drozdowska, A. Owens, K. Kamada, K. Tsutsumi, Y. Usuki, T. Yanagida, and A. Yoshikawa, IEEE Trans. Nucl. Sci. **55**, 2420–2424 (2008).
- ¹²W. Moses, M. Weber, S. Derenzo, D. Perry, P. Berdahl, and L. Boatner, IEEE Trans. Nucl. Sci. **45** (1998).
- ¹³G. F. Knoll, *Radiation detection and measurement* (Wiley, New York, 2010).
- ¹⁴P. Antonini, S. Belogurov, G. Bressi, G. Carugno, and D. Iannuzzi, Nucl. Instrum. Meth. A **486**, 799–802 (2002).
- ¹⁵W. F. Krupke, IEEE J. Quant. Electron. , 20 (1965).
- ¹⁶J. C. Wright, D. J. Zalucha, H. V. Lauer, D. E. Cox, and F. K. Fong, J. Appl. Phys. **44**, 781 (1973).
- ¹⁷L. Barcellan, E. Berto, G. Carugno, G. Galet, G. Galeazzi, and A. F. Borghesani, Rev. Sci. Instrum. **82**, 95103 (2011).
- ¹⁸Y. Zorenko, V. Gorbenko, T. Zorenko, V. Savchyn, M. Bantenschuk, A. Osvet, and C. Brabec, J. Lumin. **154**, 198–203 (2014).
- ¹⁹“physics.nist.gov/PhysRevData/Star/Text/method.html,”.
- ²⁰M. Eichhorn, S. T. Fredrich-Thornton, E. Heumann, and G. Huber, Appl. Phys. B **91**, 249 (2008).
- ²¹S. Payne, L. Chase, L. K. Smith, W. L. Kway, and W. F. Krupke, IEEE J. Quant. Electron. **28**, 2619–2630 (1992).
- ²²N. Ter-Gabrielyan, M. Dubinskii, G. A. Newburgh, A. Michael, and L. D. Merkle, Opt. Express **17**, 7159 (2009).
- ²³O. Toma and S. Georgescu, IEEE J. Quant. Electron. **42**, 192 (2006).
- ²⁴L. Esterowitz, J. N. A. Schnitzler, and J. Bahler, Appl. Opt. **7**, 2053 (1968).
- ²⁵E. Brown, C. B. Hanley, U. Hömmerich, A. G. Bluiett, and S. B. Trivedi, J. Lumin. **133**, 244–248 (2013).
- ²⁶F. Auzel, Chem. Rev. **104**, 139–173 (2004).